

# Evaluation of Metronidazole Tablets Formulated With Different Disintegrants Using Moisture Activated Dry Granulation (MADG)

Ezegbe Chekwube Andrew<sup>1,\*</sup>, Ezegbe Amarachi Grace<sup>2</sup>, Chime Amarachi Salome<sup>1</sup>, Ugwu Calister Elochukwu<sup>1</sup>, Boniface Christian Izuchukwu<sup>1</sup>, Ugwuoke Kenneth Ejiofor<sup>1</sup>, Chukwuemeka Chizoba Lorrita<sup>1</sup>, Onunkwo Godswill<sup>1</sup>

<sup>1</sup>Department of Pharmaceutical Technology and Industrial Pharmacy, University of Nigeria, Nsukka-410001, Enugu State, Nigeria

<sup>2</sup>Department of Home Science and Management, University of Nigeria, Nsukka-410001, Enugu State, Nigeria

## ABSTRACT

**Introduction:** Metronidazole is a synthetic oral nitroimidazole antibiotic used in the treatment of infections caused by anaerobic bacteria and protozoa. It also has amebicidal and antiprotozoal properties. **Aim:** The purpose of the study was to formulate and evaluate metronidazole tablets formulated with polymers (PVP and PEG) and maize starch as disintegrant using moisture activated dry granulation (MADG). **Method:** Twenty-four (24) batches of metronidazole granules and tablets were prepared by moisture activated dry granulation. Metronidazole (200 mg), lactose and gelatin (1,2,4 and 8 %) were mixed, followed by continuous mixing. Prior to compression, micro-crystalline cellulose, disintegrants and magnesium stearate were added. The dried granules were passed via 1.0 mm sieve after which they were labelled and stored in an air tight container. All other batches were also similarly prepared. **Result:** The result showed that the mean weight of the tablets ranged from  $0.33 \pm 0.01$  to  $0.35 \pm 0.04$  g. Tablet hardness ranged from  $5.00 \pm 0.85$  to  $6.36 \pm 1.43$ . The results showed that batch 11 tablets had higher crushing strength than batch 24 with a significant difference. Table 2 shows the hardness test results and clearly indicates that the results of all the samples significantly differ from each other ( $p < 0.05$ ). The tablet friability test ranged from  $0.21 \pm 0.17$  for batch 24 and  $0.60 \pm 0.16$  for batch 11. The formulated tablets showed average disintegration time ranges from  $0.52 \pm 0.01$  to  $14.03 \pm 0.03$ . According to USP, the disintegration time must be in the range of 15 min for uncoated tablets, and 30 mins for film coated tablets. **Conclusion:** The study established that polyethylene glycol and polyvinyl pyrrolidone polymers had better dissolution profile than maize starch which has the best disintegration properties.

**Keywords:** Metronidazole, Moisture Activated Dry Granulation, Disintegrants, Polymers.

## Vol No: 07, Issue: 02

Received Date: March 13, 2023

Published Date: April 03, 2023

### \*Corresponding Author

**Ezegbe Chekwube Andrew**

Department of Pharmaceutical Technology and Industrial Pharmacy, University of Nigeria, Nsukka-410001, Enugu State, Nigeria, Tel: 2348038042802

**E-mail:** Deepakdalal.hps@gmail.com

**Citation:** Ezegbe CA, et al. (2023). Evaluation of Metronidazole Tablets Formulated With Different Disintegrants Using Moisture Activated Dry Granulation (MADG). Mathews J Pharma Sci. 7(2):18.

**Copyright:** Ezegbe CA, et al. © (2023). This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

## INTRODUCTION

Metronidazole is a synthetic oral nitroimidazole antibiotic used in the treatment of infections caused by anaerobic bacteria and protozoa [1]. It also has amebicidal and antiprotozoal properties. It is more soluble in alcohol and water. Its mechanism of action is based on the prevention of nucleic acid synthesis by destroying microbial cell DNA [2]. Metronidazole exists in different forms such as white-to-white, circular, biconvex and film coated tablets. The drug has a molecular formula of  $C_6H_9N_3O_3$ , a molecular weight of 171.15 g/mol, a melting point of 159-163 °C and a biological half-life of 8 h.

Oral delivery of the drug is the most preferred route of drug administration due to the ease of administration, patient compliance and flexibility in the formulations [3,4]. Two major factors determine the clinical effectiveness of tablet formulations. They are the ability of the drug to be present in the labelled amount and its availability to the body [5]. An oral tablet is meant to deliver the drug to the human body via the gastro-intestinal system in order to produce a therapeutic effect [6-8]. It had been reported that in many situations, the bioavailability of drugs from different manufacturers did not give the same therapeutic response [9]. Medicines with poor quality do not meet official standards for strength, quality, purity, packaging and labeling. Serious health implications are usually associated with counterfeit and substandard drugs [10].

Metronidazole is administered via different routes like rectal, topical, intravenous, oral and vaginal with different bioavailability percentages ranging from 80 % (oral), 60-80 % (rectal), and 20-25 % (vaginal) [11]. Adverse drug reactions associated with metronidazole include nausea, diarrhea, weight loss, abdominal pain, vomiting, headache, dizziness and metallic taste in the mouth [11].

Moisture activated dry granulation (MADG) is a process where granules are created with water and a granulating binder, but are not heat dried or milled. There are two stages associated with the MADG. The agglomeration and moisture distribution

[12]. MADG was developed in response to the difficulties experienced with wet granulation in terms of endpoint, drying and milling. Wet granulation endpoint is very sensitive to granulation time and shear. The wet granules need to be dried to a narrow range of moisture contents, which is difficult. The dried granules need to be milled, but the milled granules often have either too many fines or too many coarse particles.

During agglomeration, a major portion of the formulation containing the drug is agglomerated. The drug is blended with filler and binder in powder form, which constitutes approximately 50-80 % of the formula weight. In the moisture distribution stage, a small amount of water is sprayed as small droplets onto the blend. Water moistens the blend and causes the binder to become tacky, which causes particles, to form moist agglomerates. This process does not create large granules, which would need milling, and because very little water is used in the process, the endpoint is not sensitive to blending [13].

## MATERIALS AND METHODS

### Materials

Metronidazole was obtained from Evans Pharmaceutical Company, England. Gelatin was obtained from May and Baker, Lagos. Magnesium stearate and lactose was procured from Ludwigshafen, Germany. All other reagents and solvents used were analytical grade.

### Methods

#### Preparation of metronidazole granules and tablets using moisture activated dry granulation

Twenty-four (24) batches of metronidazole granules and tablets were prepared by moisture activated dry granulation according to the formula in Table 1 [14]. Metronidazole (200 mg), lactose and gelatin (1, 2, 4 and 8 %) were mixed, followed by continuous mixing. Prior to compression, micro-crystalline cellulose, disintegrants and magnesium stearate were added. The dried granules were passed via 1.0 mm sieve after which they were labelled and stored in an air tight container. All other batches were also similarly prepared.

**Table 1.** Formula used in the preparation of 24 batches of metronidazole

Ingredients	1	2	3	4	5	6	7	8	9	10	11	12	13	14	15	16	17	18	19	20	21	22	23	24
Metronidazole	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2	0.2
Lactose (g)	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35
Gelatin (g)	0.35	0.0035	0.0035	0.0035	0.0035	0.0035	0.07	0.07	0.07	0.07	0.07	0.014	0.014	0.014	0.014	0.014	0.014	0.028	0.028	0.028	0.03	0.028	0.028	0.028
PVP (g)	0.35	0.007	-	-	-	-	0.035	0.07	-	-	-	-	0.035	0.07	-	-	-	-	0.035	0.07	-	-	-	-
PEG (g)	-	-	0.035	0.07	-	-	-	-	0.035	0.07	-	-	-	-	0.035	0.07	-	-	-	-	0.04	0.07	-	-
Maize starch	-	-	-	-	0.0108	0.035	-	-	-	-	0.018	0.035	-	-	-	-	0.0108	0.035	-	-	-	-	0.0108	0.035
Magnesium stearate	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35	0.35
Micro crystalline cellulose	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01	0.01

## Evaluation of granule properties

### Determination of angle of repose

A plastic funnel in ring-supported by a retort stand. A sheet of paper was placed below the funnel assembly. A sheet of fibre board was placed below the funnel orifice making sure it fits tightly. 30.0 g quantity of the powder was transferred into the funnel. The fibre sheet was drawn away and the timer simultaneously started. The timer was stopped when all of the powder had passed through the funnel. The height of the heap was measured using a graduated ruler. A pencil was used to outline the base of the contour. The angle of the conical heap so formed was determined from equation 8. The powder was returned to the funnel and the experiment was repeated thrice [15]:

$$\tan \theta = \frac{\text{height of powder heap, (h)}}{\text{radius of powder heap, (r)}} \quad - \quad - \quad - \quad (1)$$

### Bulk density

A weighed quantity of powder (20.0 g) was placed in a 100-ml graduated cylinder. The cylinder was gently dropped onto a wooden surface three times from a height of one inch at 2 sec interval. The volume assumed after the treatment was taken as the bulk volume. The experiment was repeated thrice [16]:

$$\text{Bulk density (g / ml)} = \frac{\text{mass}}{\text{bulk volume}} \quad - \quad - \quad - \quad (2)$$

### Tapped density

A weighed quantity (20.0 g) of the powder was placed in a 100-ml graduated cylinder. The cylinder was tapped up to 500 times on the wooden surface or to a constant volume. The final volume attained represents the tapped volume. The experiment was repeated thrice [16]:

$$\text{Tapped density (g / ml)} = \frac{\text{mass}}{\text{tapped volume}} \quad - \quad - \quad - \quad (3)$$

### Hausner's quotient

The Hausner ratio (HR), defined as the ratio of tapped to bulk densities. It is a common technique widely used to describe the packing behavior of powders when they are subjected to tapping [13]:

$$\text{Hausner ratio} = \frac{\text{tapped density}}{\text{bulk density}} \quad - \quad - \quad - \quad (4)$$

### Determination of percentage fines

The granules were shaken through a 0.1 mm sieve and fine particles were obtained. The weight of the fines were

measured and expressed as the percentage of the total weight of granules.

$$\text{Percentage weight} = \frac{\text{weight of fines}}{\text{Total weight of granules}} \times 100 \quad - \quad - \quad (5)$$

### Tablet compression

The dried and screened granules were separated into fine and coarse particles. The fines were then lubricated with 1 % w/w concentrations of magnesium stearate and mixed with the coarse particles. The granules were compressed into tablets using F-3 Manesty single punch tableting machine fitted with 9.5 mm flat faced tooling. Compression pressure was maintained at 47 to 55 N [16].

### Evaluation of tablets

#### Hardness test

Ten (10) tablets were randomly selected from each batch. Using the Monsanto tester, the pointer was fixed at 0 Kgf. One tablet was held and placed with the tester holder and the screw adjusted until the pressure applied cracked the tablet. The hardness of each tablet was determined and recorded [17].

#### Uniformity of weight

Twenty (20) tablets were randomly selected from each batch. Using the analytical balance (120-5DM, S. Mettler, Germany), the 20 tablets were weighed together. The mean tablet weight was then calculated. Subsequently the tablets were weighed individually and the weights of the tablets were recorded. The variations of individual tablet weights from the mean weight were determined, and the percentage deviations calculated [17]:

$$\text{Percentage deviation} = \frac{\text{Deviation}}{\text{Mean weight}} \times 100 \quad - \quad - \quad (6)$$

#### Tablet friability

Ten (10) tablets were selected at random from each batch. Subsequently, they were dedusted and accurately weighed together in an analytical balance. The dedusted tablets were then placed into the friabilator which was set to rotate at 25 rpm for 4 min. Then the tablets were removed, dedusted and re-weighed. The mean loss in weight and percent friability was then calculated. The friability test was repeated 3 times. The mean and standard deviation were then calculated [ ]:

$$\text{Friability test} = \frac{\text{initial weight} - \text{final weight}}{\text{initial weight}} \times 100 - \quad - (7)$$

### Disintegration test

Six (6) tablets were selected at random from each batch using the Erweka disintegrating unit and distilled water as the disintegrating medium maintained at  $37 \pm 1.0$  °C. One tablet was placed into each tube of the disintegrating unit. The time taken for each tablet to completely break down to particles and pass through the wire mesh was recorded. The mean disintegration time and standard deviation from each batch was calculated [17].

### Dissolution studies

The in-vitro drug release studies were carried out using tablet dissolution test apparatus (Erweka DT-D, Heusentamm, Germany) [18]. Initially, 900 ml of 0.1 N HCl at (pH 1.2) was used as the dissolution medium for 2 h at 50 rpm, maintained at  $37 \pm 1.0$  °C. Samples were withdrawn at 5, 10, 20, 40, 60, 80, 100 and 120 min intervals and replaced with fresh equal volumes of the dissolution media maintained at the same temperature. From the Beer's calibration curve, the concentration of each drug released over time was calculated. The percentage amount of metronidazole released for each batch was plotted against time [18].

### Data analysis

All the measurements were repeated at least thrice and the data obtained analyzed by Student t-test and One-Way Analysis of Variance (ANOVA). Statistical analysis was performed using Statistical Product and Services Solution software (SPSS, version 22.0 Inc., Chicago IL, USA) and Excel Microsoft Office version 2012. The results were presented as mean  $\pm$  SD, and statistical differences between means considered significant at ( $p < 0.05$ ).

### RESULTS AND DISCUSSION

The angle of repose is also indicative of flow rate [19]. It is important to note that in tableting, an angle of repose of 25, shows excellent flow, 25-30 shows good flow, 30-40 shows passable, while  $> 40$  shows poor flow. All the batches could be said to possess good flow since the angle of repose was within the ranges of  $24 \pm 25.0$  to  $35 \pm 32.3$  (Table 2). Hausner's ratio and Carr's index are both indirect means of assessing the flow properties of granules. The Hausner's ratios were within the ranges of  $1.06 \pm 0.02$  and  $1.26 \pm 0.02$ , while Carr's index were within the ranges of  $6.55 \pm 0.13$  and  $24.00 \pm 1.00$  [20]. Tapped density is a function of particle size and size distribution. The tapped density of the metronidazole granule ranged from  $0.45 \pm 0.01$  to  $0.82 \pm 0.02$ . The size of the particles affects it, as decrease particle size leads to increase tapped density and vice versa [20].

**Table 2.** Micromeritic and flow properties of metronidazole granules

Batches	Tapped density (g/cm <sup>3</sup> ) mean $\pm$ SD	Angle of repose (°) mean $\pm$ SD	Flow rate (g/s) mean $\pm$ SD	Hausners Ratio mean $\pm$ SD	Carrs index (%) mean $\pm$ SD	Percentage fines. Mean $\pm$ SD
1	$0.82 \pm 0.02$	$29 \pm 27.3$	$9.33 \pm 0.15$	$1.16 \pm 0.01$	$16.66 \pm 1.52$	$20.23 \pm 0.01$
2	$0.56 \pm 0.02$	$24 \pm 25.0$	$6.90 \pm 0.10$	$1.26 \pm 0.02$	$13.83 \pm 0.15$	$20.50 \pm 0.13$
3	$0.62 \pm 0.02$	$32 \pm 30.3$	$6.21 \pm 0.01$	$1.21 \pm 0.02$	$10.94 \pm 0.04$	$20.74 \pm 0.01$
4	$0.65 \pm 0.02$	$28 \pm 28.3$	$8.13 \pm 0.01$	$1.15 \pm 0.02$	$10.74 \pm 0.04$	$20.17 \pm 0.01$
5	$0.68 \pm 0.01$	$30 \pm 30.6$	$9.76 \pm 0.01$	$1.15 \pm 0.01$	$8.76 \pm 0.11$	$21.07 \pm 0.01$
6	$0.67 \pm 0.01$	$34 \pm 31.7$	$7.25 \pm 0.01$	$1.12 \pm 0.01$	$7.62 \pm 0.24$	$20.24 \pm 0.02$
7	$0.55 \pm 0.01$	$27 \pm 26.0$	$10.06 \pm 0.01$	$1.07 \pm 0.01$	$10.80 \pm 0.10$	$21.44 \pm 0.02$
8	$0.55 \pm 0.04$	$30 \pm 28.3$	$8.36 \pm 0.01$	$1.12 \pm 0.01$	$15.74 \pm 0.04$	$22.48 \pm 0.04$
9	$0.62 \pm 0.02$	$30 \pm 29.0$	$7.15 \pm 0.01$	$1.16 \pm 0.02$	$15.62 \pm 0.01$	$24.22 \pm 0.04$

10	0.64 ± 0.01	31 ± 29.3	6.57 ± 0.21	1.18 ± 0.01	13.83 ± 0.02	23.52 ± 0.03
11	0.61 ± 0.01	31 ± 29.6	8.06 ± 0.02	1.15 ± 0.01	7.92 ± 0.02	22.46 ± 0.23
12	0.62 ± 0.02	33 ± 31.3	7.15 ± 0.01	1.07 ± 0.01	6.55 ± 0.13	24.29 ± 0.03
13	0.53 ± 0.02	27 ± 27.0	7.65 ± 0.03	1.06 ± 0.02	21.55 ± 0.05	23.23 ± 0.01
14	0.52 ± 0.02	27 ± 26.7	10.35 ± 0.03	1.26 ± 0.02	24.00 ± 1.00	21.45 ± 0.02
15	0.57 ± 0.02	32 ± 29.3	8.04 ± 0.01	1.31 ± 0.01	23.64 ± 0.13	20.11 ± 0.02
16	0.56 ± 0.01	30 ± 27.7	7.10 ± 0.01	1.30 ± 0.01	17.53 ± 0.03	20.82 ± 0.02
17	0.48 ± 0.01	33 ± 30.0	6.24 ± 0.02	1.20 ± 0.01	14.30 ± 0.01	25.02 ± 0.04
18	0.52 ± 0.02	27 ± 27.0	9.62 ± 0.03	1.16 ± 0.01	12.66 ± 0.57	24.76 ± 0.58
19	0.46 ± 0.01	32 ± 28.7	8.21 ± 0.01	1.26 ± 0.01	19.48 ± 0.01	21.03 ± 0.05
20	0.45 ± 0.01	30 ± 28.0	8.36 ± 0.01	1.24 ± 0.01	21.66 ± 2.08	21.68 ± 0.04
21	0.48 ± 0.01	29 ± 28.7	9.12 ± 0.02	1.25 ± 0.01	14.31 ± 0.03	22.12 ± 0.09
22	0.47 ± 0.01	35 ± 32.3	10.11 ± 0.01	1.25 ± 0.01	14.54 ± 0.04	23.07 ± 0.77
23	0.52 ± 0.02	34 ± 32.3	9.22 ± 0.03	1.18 ± 0.01	21.47 ± 0.08	23.12 ± 0.81
24	0.53 ± 0.01	30 ± 30.7	7.05 ± 0.01	1.17 ± 0.01	18.84 ± 0.03	24.25 ± 0.36

**Table 3.** Physicochemical properties of metronidazole tablets

Batches	Weight uniformity mean ± SD	Friability mean ± SD	Hardness mean ± SD	Disintegration mean ± SD
1	0.33 ± 0.01	0.90 ± 0.17	5.30 ± 0.85	1.39 ± 0.08
2	0.34 ± 0.01	0.60 ± 0.21	5.85 ± 1.35	0.63 ± 0.04
3	0.34 ± 0.01	0.69 ± 0.17	5.00 ± 0.85	0.62 ± 0.53
4	0.34 ± 0.01	0.69 ± 0.28	5.40 ± 1.59	0.57 ± 0.08
5	0.33 ± 0.01	0.73 ± 0.22	5.20 ± 1.01	0.52 ± 0.06
6	0.34 ± 0.01	0.60 ± 0.09	5.75 ± 1.23	0.47 ± 0.01
7	0.33 ± 0.01	0.57 ± 0.09	5.60 ± 0.57	5.23 ± 0.01
8	0.33 ± 0.01	0.45 ± 0.13	5.70 ± 1.34	2.27 ± 0.01
9	0.32 ± 0.01	0.52 ± 0.29	5.70 ± 1.34	1.32 ± 0.01
10	0.34 ± 0.01	0.53 ± 0.29	6.35 ± 1.16	1.07 ± 0.02
11	0.34 ± 0.01	0.60 ± 0.16	6.36 ± 1.43	1.13 ± 0.01
12	0.34 ± 0.01	0.42 ± 0.21	6.00 ± 1.16	1.08 ± 0.01
13	0.35 ± 0.02	0.39 ± 0.16	5.60 ± 1.17	8.21 ± 0.02
14	0.34 ± 0.01	0.36 ± 0.16	5.70 ± 1.27	7.55 ± 0.04
15	0.34 ± 0.01	0.34 ± 0.15	5.30 ± 1.01	14.07 ± 0.04

16	0.34 ± 0.01	0.50 ± 0.25	5.55 ± 1.19	0.54 ± 0.02
17	0.34 ± 0.01	0.44 ± 0.20	5.80 ± 1.23	0.67 ± 0.01
18	0.34 ± 0.01	0.19 ± 0.11	5.50 ± 1.52	14.03 ± 0.03
19	0.34 ± 0.02	0.22 ± 0.18	6.05 ± 0.89	2.53 ± 0.04
20	0.34 ± 0.02	0.29 ± 0.15	6.04 ± 0.89	1.14 ± 0.03
21	0.33 ± 0.02	0.26 ± 0.15	5.50 ± 1.52	2.20 ± 0.01
22	0.34 ± 0.02	0.26 ± 0.17	5.50 ± 1.53	2.20 ± 0.01
23	0.34 ± 0.02	0.21 ± 0.17	6.03 ± 0.89	1.14 ± 0.03
24	0.34 ± 0.02	0.21 ± 0.17	5.40 ± 1.53	1.14 ± 0.03

Table 3 shows the results of the weight uniformity test carried out on the metronidazole tablets. The result showed that the mean weight of the tablets ranged from  $0.33 \pm 0.01$  to  $0.35 \pm 0.04$  g. The weight uniformity test was performed on the tablets to determine its compliance with USP specifications. All the tablets passed the weight uniformity test as the percentage of weight deviation was within the USP limits of  $\pm 5\%$  of average weight. The BP stipulates that tablets with an average weight of 250 mg or more should have percentage deviation not greater than  $5\%$  [21]. According to Mizanur et al, the metronidazole tablets meet the USP specification [22].


The hardness was carried out using the Mosanto hardness tester. The result of the hardness test of metronidazole tablets are shown in Table 3. Tablet hardness ranged from  $5.00 \pm 0.85$  to  $6.36 \pm 1.43$ . The results showed that batch 11 tablets had higher crushing strength than batch 24 with a significant difference. Table 3 shows the hardness test results and clearly indicates that the results of all the samples significantly differ from each other ( $p < 0.05$ ). Tablet hardness is an important parameter in drug availability because it affects the dissolution rates of drugs and friability. The tablet formulations were within the ranges of 4 to 8 Kgf [23].

Friability test is used to determine the resistance of tablets to abrasion [23]. It is an important parameter in tablet handling, packaging and transportation. It is used to determine the physical strength of compressed and uncoated tablets upon exposure to mechanical shock and attrition. According to Rahman et al, all the brands met the friability specification


[24]. The results of the friability test are shown in Table 3. The tablet friability test ranged from  $0.21 \pm 0.17$  for batch 24 and  $0.60 \pm 0.16$  for batch 11.

Disintegration test was carried out under USP specifications [23]. The formulated tablets showed average disintegration time ranges from  $0.52 \pm 0.01$  to  $14.03 \pm 0.03$ . According to USP, the disintegration time must be in the range of 15 min for uncoated tablets, and 30 mins for film coated tablets [23]. According to Rahman et al, all the brands met the requirement as the disintegration time was found to be between the ranges of  $7.25 \pm 0.69$  to  $17.0 \pm 0.63$  mins [24]. All the tablets passed the disintegration test.


Dissolution of a drug tablet is an important step which leads to the absorption of the drug in the body. The disintegration process breaks the intact tablets into smaller particles thus increasing the surface area thereby increasing absorption. According to BP specification, at 45 min, not less than 70 % of the prescribed or stated amount of the active ingredient should have been released at the completion of dissolution test. The dissolution profile shows that none of the formulations released all its drug content within the 120 min test period. For film coated metronidazole tablets, drug release should not be less than 85 % of labelled amount in 60 min [23]. According to Rahman et al, their brand Metro-04 had maximum drug release within 60 min (98.87 %), while brand Metro-02 had minimum drug release (85.34 %) within the same time interval [24].

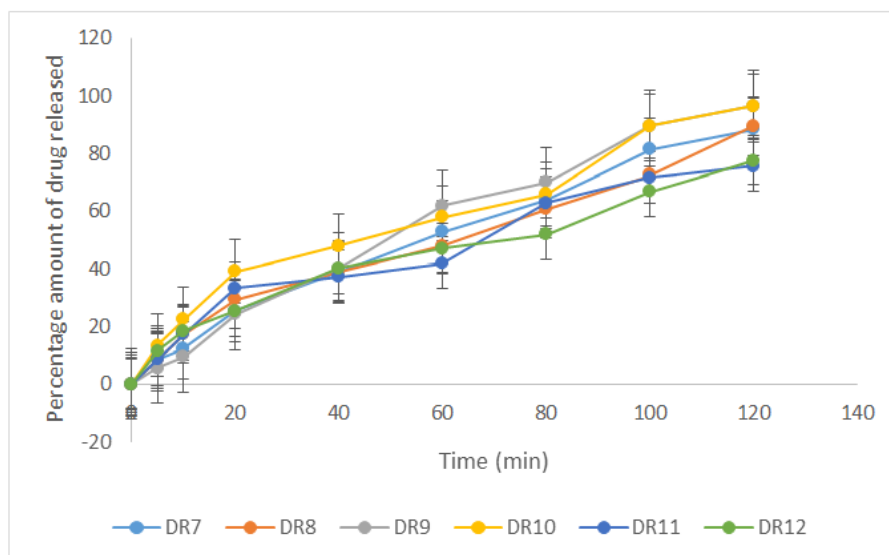

**Figure 1.** Percentage drug release of tablet containing 2 % binder concentration.

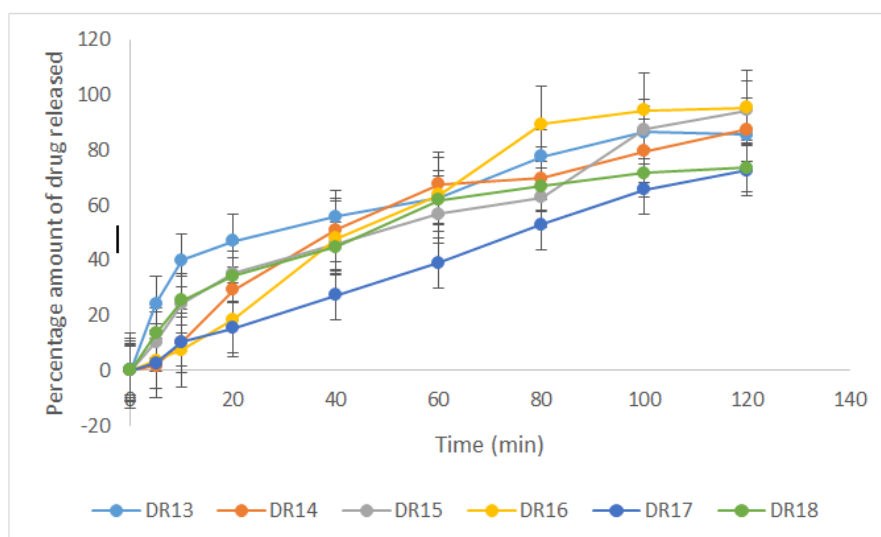

**Figure 2.** Percentage drug release of tablet containing 4 % binder concentration.

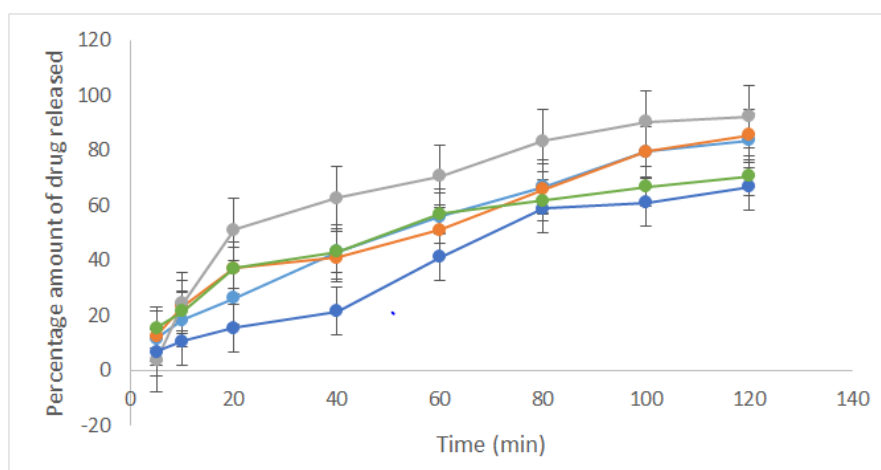

**Figure 3.** Percentage drug release of tablet batches containing 8 % binder concentration.



**CONCLUSION**

Metronidazole was successfully formulated using the moisture activated dry granulation method. The tablet had good granules and tablet properties. The hardness, friability and disintegration time were within the stipulated limits in the compendia.

**CONFLICT OF INTEREST**

Authors declared no conflict of interest.

**REFERENCES**

- Shilpa PC, Pradeep SP. (2012). Pharmaceutical excipients: A review. *Int J Adv Pharm Biol Chem.* 1(1):21-34.
- Das AS, Das S, Samanta A. (2013). Formulation and evaluation of controlled release floating capsules of ciprofloxacin HCL. *Der Pharm Sin.* 4(2):72-75.
- Chukwu A. (1994). Studies on detarium microcarpium gum II. Investigation as a prolonged release matrix for encapsulated chlorpheniramine maleate. *STP Pharma Sci.* 4:399-403.
- Disanto AR. (1995). Bioavailability and bioequivalency testing in remington. *Sci Pract Pharm.* 19:606.
- Eichie FE, Amalime AE. (2007). Evaluation of the binder effects of the gum mucilages of *Cissus populinea* and *Acacia senegal* on the mechanical properties of paracetamol tablets. *Afr J Biotechnol.* 6(19):2208-2211.
- Emeje M, Isimi C, Kunle O. (2007). Effect of *Grewia* gum on the mechanical properties of paracetamol tablet formulations. *Afr J Pharm Pharmacol.* 1(1):1-6.
- Ibezim EC, Ofoefule SI, Omeje EO, Onyishi VI, Odoh UE. (2008). The role of ginger starch as a binder in acetaminophen tablets. *Sci Res Essay.* 3(2):46-50.
- Jani JK, Shah DP, Jain VC, Patel MJ, Vithalan DA. (2007). Evaluating mucilage from *Aloe barbadensis* Miller as a pharmaceutical excipient for sustained release matrix tablets. *Pharm Technol.* 31(11):90-98.
- Hamman JH. (2008). Composition and applications of *Aloe vera* leaf gel. *Molecules.* 13(8):1599-1616.
- Kotke MK, Chueh HR, Rodes CT. (1992). Comparison of disintegrant and binder activity of three corn starch products. *Drug Dev Ind Pharm.* 18(20):2207-2223.
- Prescott JK, Barnum RA. (2000). Powder flowability. *Pharm Technol.* 24:60-84.
- Sharma A, Sethi P, Pawar D. (2011). Granulation techniques and innovations. *Inventi Rapid: Pharmtech.* 10.
- Aniruddha MR, Joseph BS. (2001). Use of a moist granulation technique to develop controlled-release dosage forms of acetaminophen. *Drug Dev Ind Pharm.* 27(4):337-343.
- Venkateswara Reddy B, Navaneetha K, Sandeep P. (2014). Improved tablet production by modified granulation techniques, *International Journal of research in pharmacy and life sciences.* 2(2):224-235.
- Das S, Roy D. (2016). Formulation and evaluation of beta-cyclodextrin complex tablets of ibuprofen. *Int J Pharm Res Health Sci.* 4(1):1022-1024.
- Nag D, Das S, Samanta A. (2015). Formulation and evaluation of immediate release tablet of isoniazid and pyridoxine hydrochloride. *World J Pharm Pharm Sci.* 4:1726-1740.
- Haritha B. (2017). A review on evaluation of tablets. *J Formul Sci Bioavailab.* 1:2-3.
- Das S, Samanta A, Dey HS. (2015). Formulation, in vitro release kinetics and stability interpretation of sustained release tablets of metformin hydrochloride. *Int J Pharm Pharm Sci.* 7(3):418-22.
- Eziuzo OS, Emmanuel A, Naomi BO, Joel OO. (2015). Modification of drug release profile of metronidazole tablet using co-precipitate of *Irvingia* and egg albumin—A proven good technology. *World J Pharm Sci.* 3(3):588-595.
- Vijay K, Maria de la Luz RM, Yang D. (2002). Preparation, characterization, and tableting properties of a new cellulose-based pharmaceutical aid. *International journal of pharmaceutics.* 235(1-2):129-140.
- United States Pharmacopeia. (2006). United States Pharmacopeial Convention Inc. Rockville.
- Lavanya K, Senthil V, Rathi V. (2011). Pelletization technology: a quick review. *IJPSR.* 2(6):1337-1355.
- Noor S, Salam FBA, Hima HN, Bhuiyan MSI, Chowdhury S. (2017). Comparative in-vitro quality evaluation of some brands of metronidazole tablet available in Bangladesh. *Int J Appl Res.* 3(7):753-758.
- United States Pharmacopeia National Formulary, the United States Pharmacopeial Convention. Inc., Rockville, MD, 2008.